

Sol-Gel Preparation of Pd Nanoparticle over γ -Al₂O₃ and its Application in Hydrogenation of Nitrobenzene

Hekmat Abdollah¹

Department of Chemistry, Kabul University, Afghanistan

Received: 09 January 2020

Accepted: 23 February 2020

Published: 01 March 2020

Abstract

Aniline was synthesized by catalytic hydrogenation of nitrobenzene (NB) on nano-sized Pd on γ -Al₂O₃ catalyst prepared by sol-gel method. The catalyst was characterized by SEM and XRD. The average particle of Pd catalyst was 36 nm. In hydrogenation reaction of nitrobenzene, the hydrogenation rate was zero-order with respect to nitrobenzene and increased with increasing of hydrogen pressure. Compared with commercial Pd/ γ -Al₂O₃, catalytic activity and selectivity of the as-prepared Pd/ γ -Al₂O₃ is superior. The reason proposed for higher catalytic activity of nano-sized Pd is the small particle size and high density surface defects.

Keywords: Nitrobenzene; Aniline; Nano-sized Pd on γ -Al₂O₃; Catalytic Hydrogenation.

How to cite the article:

H. Abdollah, Sol-Gel Preparation of Pd Nanoparticle over γ -Al₂O₃ and its Application in Hydrogenation of Nitrobenzene, Medbiotech J. 2020; 4(1): 036-039, DOI: 10.22034/mbt.2020.105890.

©2020 The Authors. This is an open access article under the CC BY license

1. Introduction

Aniline is a commercially important intermediate for the manufacturing of polyurethane (used in production of MDI, resin foams, automotive coating, shoe soles, spring components and rubber processing chemicals), herbicides, dyes and pigments, specialty fibers and drugs [1]. Aniline can be simply produced from benzene in two steps: First, benzene is nitrated (reacted with nitric acid) to yield nitrobenzene. Second, nitrobenzene is reduced to give aniline [2]. A variety of reducing agents are effective for the reduction, including hydrogen sulfide, iron, zinc, tin and hydrogen in presence of suitable catalysts such as Pd, Pt, Ni and etc. [1, 3].

Due to Some problems (such as long time separation and potentially dangers) and the existing of BTX (Benzene, Toluene and Xylene) unit in petrochemical industry, it seems the catalytic hydrogenation is a preferred process in petrochemical industry.

Although using of palladium on activated carbon (Pd/C) leads to the highest yields in the three-phase process, however the problems such as separation and strength of the catalyst suggest that use of Pd/ γ -Al₂O₃ which has the area less than carbon [4]. It means the use of higher amount of Pd/ γ -Al₂O₃ than Pd/C.

In recent years, nanoparticles have received increasing attention since such metals exhibits a great many chemical and physical characteristics and potential technological applications. These are distinct both from those of the bulk phase and those from isolated atoms or molecules [5]. Therefore, it may seem the use of nano-sized Pd on γ -Al₂O₃ enhances the reaction yield as Pd/C.

In this research, it will be attempted to synthesize aniline from nitrobenzene over nano-sized Pd on γ -Al₂O₃ catalyst. The nano-sized Pd on γ -Al₂O₃ was prepared by sol-gel method. The textural properties of the nano-catalyst were characterized by SEM and XRD. Attention is chiefly paid to the catalytic properties of nano-sized Pd on γ -Al₂O₃ in the

¹ Corresponding author email: hekmat350@yahoo.com

synthesis of aniline from nitrobenzene, in comparison with Pd/ γ -Al₂O₃ and Pd/C. At the same time, some reasons for better catalytic properties of nano-sized Pd on γ -Al₂O₃ are proposed.

2. Experimental

2.1. Catalyst preparation and characterization

In a typical preparation of nano sized Pd on γ -Al₂O₃ sample, aluminum tri-sec butoxide (ATB) was added to sec-butanol followed by thorough mixing. A second solution, consisting H₂PdCl₄.xH₂O dissolved in warm acetone, was prepared. This Pd salt solution was added to the ATB-alcohol mixture and the solution was stirred thoroughly. A solution consisting of H₂O dissolved in methanol was added to the previous mixture containing ATB and the Pd salt. The resultant mixture was stirred at room temperature in a rotavapor. The sample was heated to 313 K and maintained at that temperature with continual stirring. The temperature was then reduced to 313 K and stirring continued for 1hr more. The sample was maintained at 333 K for 20hr with continuous stirring. The temperature was then raised to 353 K and maintained at that temperature for 1hr. Finally, the temperature was increased to 373 K and the solvent allowed to evaporate over a 30 min period. The sample was then dried in an oven at 393 K for 24 hr.

The dried sample was pretreated in a flow system using the following sequence of steps: The sample was heated in flowing He at the rate of 10 K/min to a final temperature of 773 K. Heating in He a flow rate of 30cm³/min was continued for 15 min at 773 K followed by heat treatment in O₂ at the same temperature for 2 hr and then in H₂ at 773 K for 3 hr. The H₂ was again replaced by He and the temperature increased to 793 K for 1hr. Finally, the

sample was cooled to room temperature in flowing He. Portions of the pretreated samples were sent for ICP analysis in order to determine the actual Pd loading [6].

XRD patterns were obtained on a Bruker D8 advance instrument with Pd-filtered CuK α radiation at 40kV and 30mA, employing a scanning rate of 0.05 s⁻¹ in the 2 θ range from 35 to 80°. The morphology was observed by SEM, LEO-1530VP. The mean particle size and size distribution of as-prepared Pd nanoparticles were measured by laser diffraction (Mastersizer 2000, Malvern).

2.2. Experimental set-up and procedure

The hydrogenation process was carried out in an isothermal 1L stainless steel autoclave (Buchi AG, Switzerland), which allows isothermal conditions due to a heating jacket (Figure 1). The hydrogen was supplied at the same rate that it was consumed under isobaric reaction conditions. The samples for the analysis were drawn via a sampling tube.

The experiments were carried out using the following procedure: First, nitrobenzene (Sigma Switzerland, 99%) was dissolved in a mixture of 91%wt of isopropanol (Fluka, 99%) and 9%wt distilled water. The reactor was filled with 300 mL solution and the solid catalyst (from 0.5 to 3 g) was added. Second, the reaction was initiated by removing the air from the reactor by purging with hydrogen and stirring the solution at 1500 rpm. The temperature was controlled at 323 K and the hydrogen partial pressure was kept constant between 3 and 14 bar. The samples were analyzed by a gas chromatography (GC, Perkin Elmer- 8420) with product separation in a fused silica capillary column (30m, 0.53mmID) and a FID detector.

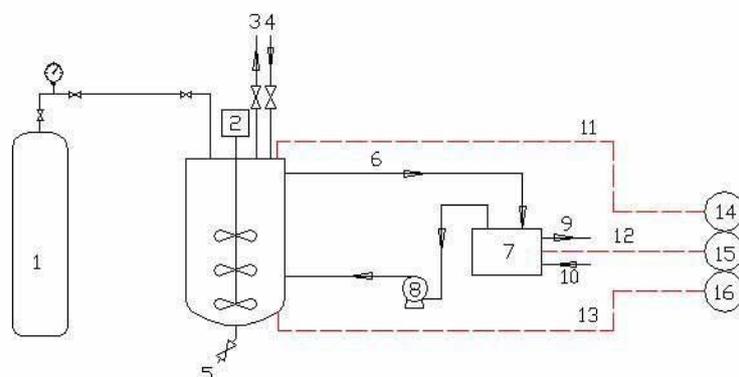


Figure 1. Experimental set up: 1-H₂ Cylinder, 2-Stirrer motor, 3-Vent, 4-Feed inlet, 5-Drainage and sampling, 6-Outlet cooled oil, 7-Oil bath, 8-Oil pump, 9-Outlet warmed water, 10-Inlet cooled water, 11-Reactor pressure signal, 12-Oil bath temperature signal, 13-Reactor pressure recorder, 14-Reactor pressure recorder, 15-Oil bath temperature recorder, 16-Reactor temperature recorder.

2.3. Catalyst characterization

The average crystalline size was estimated by the Debye-Scherrer method to be in the range of 40nm from XRD data.

The size distribution for nano-sized Pd measured by Mastersizer 2000 is shown in figure 2. The result yields an average Pd particle size of 36 nm.

The SEM micrograph of Pd nanoparticles is shown in figure 3. Individual Pd particles are spherical in shape.

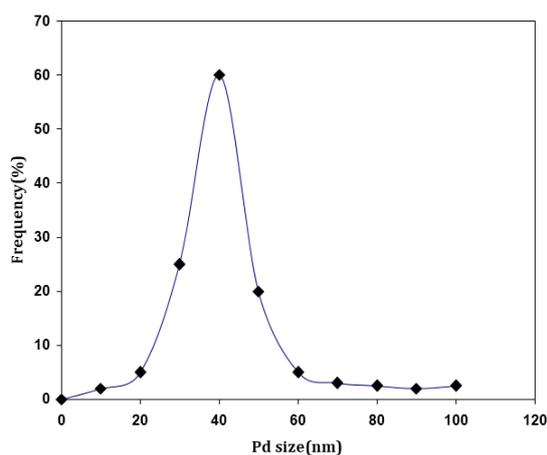


Figure 2. Size distribution of nano-sized Pd

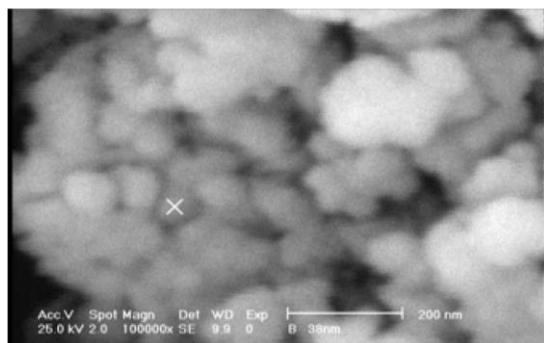


Figure 3. SEM image of nano-sized Pd particles in nano-sized Pd on γ -Al₂O₃.

3. Results and Discussion

The preliminary experiments on the hydrogenation of nitrobenzene indicated that no hydrogenation reaction occurred in the absence of the catalyst, which confirmed the absence of any noncatalytic reaction. Moreover, at a fixed temperature, the partial pressure of solvent isopropanol-water also remained constant. So, the decrease of the pressure in the reservoir vessel with time was caused only by catalytic hydrogenation of nitrobenzene to aniline. Therefore, in this manuscript catalytic activity could be expressed by hydrogenation rate defined as the amount of hydrogen consumed per minute and per gram of the nanocatalyst. The effects of nitrobenzene concentration and hydrogen pressure

on the reaction rate were investigated in the presence of Pd/ γ -Al₂O₃, nano- Pd on γ -Al₂O₃ and Pd/C; the results are shown in figures 4 and 5.

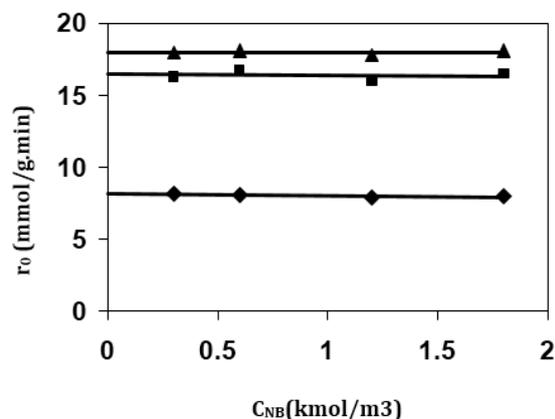


Figure 4. Effect of the concentration of nitrobenzene on initial rate. Reaction conditions: T=323 K, P=5 bar, stirring speed=1500rpm, - \blacklozenge - m_{Pd/ γ -Al₂O₃}=2.5 g/dm³, - \blacksquare - m_{nano- Pd on γ -Al₂O₃}=0.8 g/dm³, - \blacktriangle -m_{Pd/C}=2.5 g/dm³

The effect of nitrobenzene concentration on the initial rate of hydrogenation (Figure 4) shows zero-order dependence at 0.25-1.8 kmol.m⁻³ concentrations. Compared with the concentration of the hydrogen dissolved in isopropanol aqueous solution, nitrobenzene concentration might be seemed to be a constant. Therefore, the reaction rate could not change with the variation of nitrobenzene concentration. A noticeable point is the lower activity of Pd/ γ -Al₂O₃ than nano Pd on γ -Al₂O₃. The effect of hydrogenation partial pressure on the initial rate of hydrogenation was investigated at 323K in the pressure range of 3-14 bar (Figure 5). The hydrogenation rate increase with the increase of the hydrogen partial pressure. Also, it is seen more activity of nano- Pd on γ -Al₂O₃ than Pd/ γ -Al₂O₃.

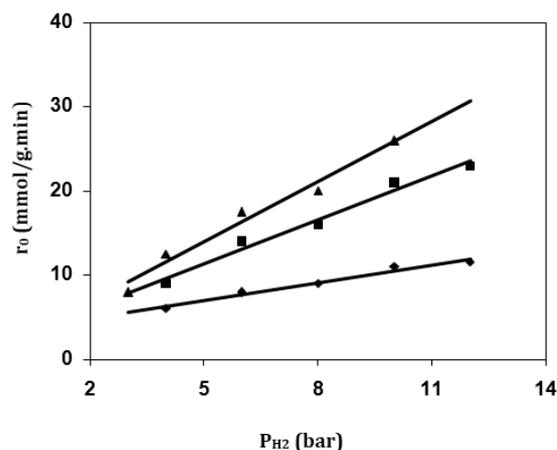


Figure 5. Effect of hydrogen partial pressure on initial rate. Reaction conditions: T=323 K, stirring speed=1500rpm, - \blacklozenge - m_{Pd/ γ -Al₂O₃}=2.5 g/dm³, - \blacksquare -m_{nano- Pd on γ -Al₂O₃}=0.8 g/dm³, - \blacktriangle -m_{Pd/C}=2.5 g/dm³

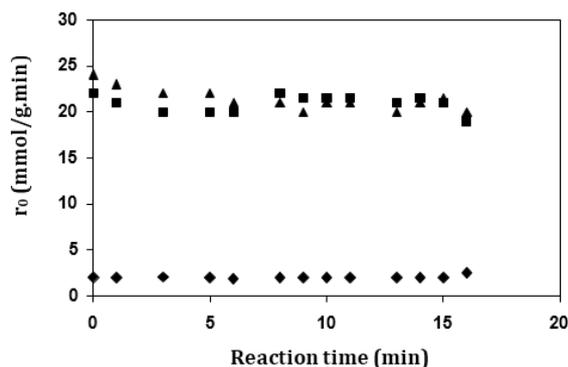


Figure 6. Correlation between catalytic activity of the catalysts. Reaction conditions: $T=323$ K, stirring speed= 1500 rpm, -◆- $m_{Pd/\gamma-Al_2O_3}=2.5$ g/dm³, -■- $m_{nano-Pd\ on\ \gamma-Al_2O_3}=0.8$ g/dm³, -▲- $m_{Pd/C}=2.5$ g/dm³

The catalytic activity comparison of the nano-sized Pd on $\gamma-Al_2O_3$ and Pd/C is shown in figure 6. The hydrogenation rate on the nano-sized Pd/ $\gamma-Al_2O_3$ is nearly the same as Pd/C at similar reaction conditions.

On the basis of similar reaction [7], it is suggested that the reason for higher catalytic activity of nano-sized Pd on $\gamma-Al_2O_3$ than Pd/ $\gamma-Al_2O_3$ is a combination effect of the small particle size and the high density surface defects.

The product of hydrogenation reaction was analyzed and it was observed that in the reaction products catalyzed by the nano-Pd on $\gamma-Al_2O_3$, no other impurity existed.

An important and attractive point in figures 4-6 is the less amount of nano-Pd on $\gamma-Al_2O_3$ than Pd/ $\gamma-Al_2O_3$ and Pd/C, so that the amount of nano-Pd on $\gamma-Al_2O_3$ is 1/3 of others (for simplicity, Pd loading in nano-Pd/ $\gamma-Al_2O_3$, Pd/ $\gamma-Al_2O_3$ and Pd/C were taken 5% measured by ICP). In other words, nanosizing Pd particles leads to the higher speed in reaction and less consumption of the as-prepared catalyst.

4. Conclusions

In this work, aniline was synthesized by catalytic hydrogenation of nitrobenzene over asprepared nano-sized Pd in a laboratory autoclave. The following results were obtained:

- 1) The average particle size of the as-prepared Pd is 36nm.
- 2) The hydrogenation rate is zero-order dependent on nitrobenzene and increases with increasing of hydrogen pressure.
- 3) The activity and selectivity of the as-prepared Pd are superior compared with those of the conventional Pd/ $\gamma-Al_2O_3$.
- 4) Also, nanosizing of Pd particles caused higher speed in reaction and less consumption of the as-prepared catalyst than conventional Pd/ $\gamma-Al_2O_3$ and Pd/C.

Notice: Now days, a series of tests are conducting by the project team on stability of the asprepared catalyst and results will be published in future.

References

1. Othmer K. 2004. Encyclopedia of Chemical Technology, Volume 2, John Wiley & Sons.
2. Beyer H., Walter W. 1997. Organic Chemistry, Albion Chemical Science Series.
3. Matsunaga F., Yasuhara M. 1988. US Patent 4987260.
4. Le J.F., Page et al. 1987. Applied heterogeneous catalysis, Edition Technip, Paris.
5. Zheng H.G., Liang J.H., Zheng J.H., Qian Y.T. 2001. Preparation of nickel nanopowders in ethanol-water system (EWS), *Mater. Res. Bull.* 36(5-6): 947.
6. Balakrishnan K., Gonzalez R.D. 1993. Preparation of Pt/Alumina Catalysts by the Sol-Gel Method, *J. Catal.* 144(2): 395-413.
7. Du Y., Chen H., Chen R. and Xu N. 2004. Synthesis of *p*-aminophenol from *p*-nitrophenol over nano-sized nickel catalysts. *Appl. Catal. A: General* 277(1-2): 259-264.